

5-2023

Experimental Investigation of the Self-Healing Potential of Bacteria for Sustainable Concrete Structures

Pitiporn Asvapathanagul
California State University, Long Beach

Simone Galano
Mineta Transportation Institute

Andrea Calabrese
California State University, Long Beach

Mehran Rahmani
California State University, Long Beach

Maggie Ly
California State University, Long Beach

See next page for additional authors

Follow this and additional works at: https://scholarworks.sjsu.edu/mti_publications



Part of the [Construction Engineering and Management Commons](#), [Industrial Engineering Commons](#), [Transportation Commons](#), and the [Transportation Engineering Commons](#)

Recommended Citation

Pitiporn Asvapathanagul, Simone Galano, Andrea Calabrese, Mehran Rahmani, Maggie Ly, Daniela Flores, Michael Hernandez, and Nicholas Banuelos. "Experimental Investigation of the Self-Healing Potential of Bacteria for Sustainable Concrete Structures" *Mineta Transportation Institute Publications* (2023). <https://doi.org/10.31979/mti.2023.2239>

This Report is brought to you for free and open access by SJSU ScholarWorks. It has been accepted for inclusion in Mineta Transportation Institute Publications by an authorized administrator of SJSU ScholarWorks. For more information, please contact scholarworks@sjsu.edu.

Authors

Pitiporn Asvathanagul, Simone Galano, Andrea Calabrese, Mehran Rahmani, Maggie Ly, Daniela Flores, Michael Hernandez, and Nicholas Banelos

Experimental Investigation of the Self Healing Potential of Bacteria for Sustainable Concrete Structures

Pitiporn Asvathanagul
Maggie Ly

Simone Galano
Daniela Flores

Andrea Calabrese
Michael Hernandez

Mehran Rahmani
Nicholas Banuelos



Mineta Transportation Institute

Founded in 1991, the Mineta Transportation Institute (MTI), an organized research and training unit in partnership with the Lucas College and Graduate School of Business at San José State University (SJSU), increases mobility for all by improving the safety, efficiency, accessibility, and convenience of our nation's transportation system. Through research, education, workforce development, and technology transfer, we help create a connected world. MTI leads the [Mineta Consortium for Transportation Mobility \(MCTM\)](#) funded by the U.S. Department of Transportation and the [California State University Transportation Consortium \(CSUTC\)](#) funded by the State of California through Senate Bill 1. MTI focuses on three primary responsibilities:

Research

MTI conducts multi-disciplinary research focused on surface transportation that contributes to effective decision making. Research areas include: active transportation; planning and policy; security and counterterrorism; sustainable transportation and land use; transit and passenger rail; transportation engineering; transportation finance; transportation technology; and workforce and labor. MTI research publications undergo expert peer review to ensure the quality of the research.

Education and Workforce

To ensure the efficient movement of people and products, we must prepare a new cohort of transportation professionals who are ready to lead a more diverse, inclusive, and equitable transportation industry. To help achieve this, MTI sponsors a suite of workforce development and education opportunities. The Institute supports educational programs offered by the

Lucas Graduate School of Business: a Master of Science in Transportation Management, plus graduate certificates that include High-Speed and Intercity Rail Management and Transportation Security Management. These flexible programs offer live online classes so that working transportation professionals can pursue an advanced degree regardless of their location.

Information and Technology Transfer

MTI utilizes a diverse array of dissemination methods and media to ensure research results reach those responsible for managing change. These methods include publication, seminars, workshops, websites, social media, webinars, and other technology transfer mechanisms. Additionally, MTI promotes the availability of completed research to professional organizations and works to integrate the research findings into the graduate education program. MTI's extensive collection of transportation-related publications is integrated into San José State University's world-class Martin Luther King, Jr. Library.

Disclaimer

The contents of this report reflect the views of the authors, who are responsible for the facts and accuracy of the information presented herein. This document is disseminated in the interest of information exchange. MTI's research is funded, partially or entirely, by grants from the California Department of Transportation, the California State University Office of the Chancellor, the U.S. Department of Homeland Security, and the U.S. Department of Transportation, who assume no liability for the contents or use thereof. This report does not constitute a standard specification, design standard, or regulation.

Report 23-04

Experimental Investigation of the Self-Healing Potential of Bacteria for Sustainable Concrete Structures

Pitiporn Asvapathanagul

Simone Galano

Andrea Calabrese

Mehran Rahmani

Maggie Ly

Daniela Flores

Michael Hernandez

Nicholas Banuelos

May 2023

A publication of the
Mineta Transportation Institute
Created by Congress in 1991

College of Business
San José State University
San José, CA 95192-0219

TECHNICAL REPORT DOCUMENTATION PAGE

1. Report No 23-04	2. Government Accession No.	3. Recipient's Catalog No.	
4. Title and Subtitle Experimental Investigation of the Self-Healing Potential of Bacteria for Sustainable Concrete Structures		5. Report Date May 2023	
		6. Performing Organization Code	
7. Authors Pitiporn Asvathanagul, PhD, PE Simone Galano, PhD Andrea Calabrese, PhD, ING, CENG, MICE Mehran Rahmani, PhD, PE Maggie Ly, BS Daniela Flores Michael Hernandez Nicholas Banuelos		8. Performing Organization Report CA-MTI-2239	
9. Performing Organization Name and Address Mineta Transportation Institute College of Business San José State University San José, CA 95192-0219		10. Work Unit No.	
		11. Contract or Grant No. ZSB12017-SJAUX	
12. Sponsoring Agency Name and Address State of California SB1 2017/2018 Trustees of the California State University Sponsored Programs Administration 401 Golden Shore, 5th Floor Long Beach, CA 90802		13. Type of Report and Period Covered	
		14. Sponsoring Agency Code	
15. Supplemental Notes			
16. Abstract Although concrete is the most widely used building material in the world, its limited tensile strength makes cracking a common phenomenon in concrete elements. This study investigates the potential of autonomous self-healing as an eco-friendly and low-cost method to increase the durability of concrete. The crack-healing potential of different types of high-alkaline-tolerant bacteria or calcite-precipitation microorganisms is investigated. High-alkaline-tolerant bacteria and calcite-precipitation microorganisms were used to retrofit lab-fractured concrete samples. The samples healed with each of these bacteria groups were cast and tested under compressive load up to failure to measure the compressive strength of the concrete samples. The outcomes of experimental tests on concrete samples healed with biological processes demonstrate how this technique can be implemented when retrofitting durability-enhanced, eco-friendly concrete structures to improve the strength of durability of the material and ultimately improve the durability of many forms of concrete infrastructure.			
17. Key Words Self-healing concrete, Bacteria-based self-healing, Durability of concrete structures, Experimental tests		18. Distribution Statement No restrictions. This document is available to the public through The National Technical Information Service, Springfield, VA 22161.	
19. Security Classif. (of this report) Unclassified	20. Security Classif. (of this page) Unclassified	21. No. of Pages 37	22. Price

Copyright © 2023

By **Mineta Transportation Institute**

All rights reserved.

DOI: 10.31979/mti.2023.2239

Mineta Transportation Institute
College of Business
San José State University
San José, CA 95192-0219

Tel: (408) 924-7560

Fax: (408) 924-7565

Email: mineta-institute@sjsu.edu
transweb.sjsu.edu/research/2239

CONTENTS

List of Figures.....	vii
List of Tables.....	viii
List of Abbreviations	ix
1. Introduction.....	1
2. Methodology	4
2.1 Bacterial Media And Growth Conditions.....	4
2.2 Biochar	6
2.3 Concrete.....	7
3. Results	11
3.1 Average Compressive Strengths.....	11
3.2 Variation of the Average Compressive Strengths	13
3.3 Elastic, Ultimate Response, and Ductility.....	16
4. Conclusions	19
Endnotes.....	21
Bibliography	24
About the Authors.....	25

LIST OF FIGURES

Figure 1. Box and Whisker Plot of Percentage of Food Wasted by Group in Municipal Solid Wastes	5
Figure 2: Humboldt HCM-500-Iha Compression Tester of the California State University Long Beach, (B) Concrete Samples After Cracking Test	10
Figure 3. Average Compressive Strengths of the Different Sets.....	12
Figure 4. Percentage Increments/Reductions of the Average Compressive Strengths of the Generic Set, Compared to Set A.....	13
Figure 5. Average Compressive Strengths of the Different Set With Standard Deviations ...	15
Figure 6. Coefficient of Variation of Each Set.....	15
Figure 7. Elastic, Peak And Ultimate Stresses Vs Strain of the Concrete Samples.....	17
Figure 8. Moduli of Elasticity of the Different Sets	18
Figure 9. Average Ductility Values of the Concrete Sets.....	18

LIST OF TABLES

Table 1. Composition of the Two Broth Cultures Used for Bacteria Growth	6
Table 2. Description of Samples Manufactured for this Study.....	8
Table 3. Summary of the Main Parameter Related to the Average Compressive Strengths ..	16

LIST OF ABBREVIATIONS

ARS: Agricultural Research Service Culture Collection

ASTM: American Society for Testing and Materials

ATCC: American Type Culture Collection

MICP: Microbially Induced Calcium-carbonate Precipitation

NRRL: North Regional Research Laboratory

NH₄-YE: Ammonium-Yeast

TYG: Tryptone-Yeast-Glucose

1. Introduction

The durability of infrastructures is defined by their ability to exceed expected design life while maintaining the desired mechanical properties without loss of serviceability. Most concrete structures have an expected service life of around 50 years. Several factors may affect their durability, such as temperature and moisture, mechanical loads, concrete permeability, and cracking. Thus, finding a way to preserve and extend the service life of concrete structures is a key task in civil engineering.

Cracking is the most common degradation phenomenon of concrete elements. Cracks may develop due to different causes, such as plastic shrinkage, expansion, settling, and overloading. Wide-open and widespread cracks increase the permeability of the concrete and facilitate the flow of potentially harmful liquids or gases. This may lead to degradation phenomena such as carbonatation, pitting, corrosion of the steel rebars, and so on.

Therefore, it is essential to limit the crack's width and diffusion. Different manual repair methods were proposed, including filling the cracks with a variety of expansive materials such as epoxy resins, polyurethane-based polymers, and latex emulsions. However, manual repairs can only be applied to visible and accessible cracks, while micro-cracks would remain unrepaired.

An innovative and relatively recent solution is self-healing (or self-repairing) concrete. Cracks may heal over time due to continued hydration of clinker minerals or carbonation of calcium hydroxide. Three self-healing general methods were studied so far:

- *Autogenous or natural self-healing.* Different natural processes can partially repair concrete cracks such as: (i) formation of calcium carbonate or calcium hydroxide, (ii) impurities, (iii) hydration of the unreacted cement, and (iv) the expansion of hydrated cementitious matrix.
- *Stimulated autogenous healing.* These methods are used when crack widths are constrained, stimulating continuous hydration or crystallization by providing a suitable addition such as mineral, crystalline admixtures, and superabsorbent polymers.
- *Autonomous self-healing.* Depends on integrating engineering modifications of the concrete matrix.

An innovative autonomous self-healing method using microbial activity has recently been introduced. Specific bacteria mixed with concrete have been seen to increase the effectiveness of self-healing. The bacteria are meant to activate and repair any damage without the need of manual intervention.⁶

Three main techniques have been studied for the optimization of microbially induced calcium carbonate precipitation (MICP), namely: (i) the direct method of incorporating the bacteria in the concrete mixture, (ii) encapsulation, and (iii) external application. The direct method is the most used and can significantly affect concrete strength.¹¹ In this method, the bacteria are usually applied within a protective material, including supplements and water, in the cement mix.^{11,12,13} Encapsulation is preferable in internal applications due to its resulting evenness and uniformity in the mixture, as well as guaranteed bacterial survival. Yet, a high rate of encapsulation could affect the compressive strength of the concrete.²⁰ External application of self-healing microorganisms entails treating the concrete surface. This could be obtained by brushing or spraying the bacteria onto the surface after clearing loose particles and spraying a safe discharge medium.²¹ The spray application has proven successful on different materials while biodeposition treatments have displayed promising results on cement-based materials.^{21,22}

A positive impact on concrete's mechanical performance was seen when using green waste-derived biochar in cementitious mixes.^{8,9} Wood waste biochar concrete has shown compressive strength of the same order as basic concrete.⁹ In similar studies, concrete with added wood and sludge waste demonstrated improved ultimate strength, suggesting that good mechanical behavior could be obtained for biochar produced by different types of waste whilst proposing safe, green, eco-friendly, and low-cost admixtures.^{8,9,10}

Although several techniques have been applied, different features still need to be investigated such as bacterial persistence, water absorption, strength reduction, and cost effectiveness/production.^{19,20} Also, proper nutrients need to be provided to the bacteria throughout the concrete's lifespan (i.e., throughout the service life of the structure).¹⁴

Furthermore, in a concrete element, cracks of different lengths, widths, depths, and locations can be detected, depending on different factors. Early-age cracks caused by drying and shrinkage are generally smaller than loading-induced ones. Consequently, the type and number of cracks to be healed need to be identified a priori. For retrofitting intervention involving self-healing mechanisms, early-age cracks appear to be the ideal candidates since the cracking period is predictable and the average crack widths are generally smaller when compared to tensile-induced ones.^{17,18}

This study evaluates the microbiological self-healing ability of Portland cement-based concrete at 28 days of curing. High-alkaline-tolerant bacteria and calcite-precipitation microorganisms were used to retrofit lab-fractured concrete. Different types of bacteria were studied in this report, namely:

- *Bacillus subtilis*. Known also as the *hay bacillus* or *grass bacillus*, this is a gram-positive bacterium commonly found in soil and the gastrointestinal tract of ruminants, humans, and marine sponges.
- *Bacillus megaterium*. A rod-shaped, gram-positive bacterium which is one of the largest eubacteria in soil.
- *Pseudomonas stutzeri*. A gram-negative soil bacterium classified as *bacillus*, or rod-shaped.
- *Sporosarcina pasteurii*. A gram-positive bacterium with the ability to precipitate calcite and solidify sand given a calcium source and urea.

The different concrete samples healed with each of these bacteria groups were cast and tested under compressive load up to failure. The compressive strengths obtained for the healed samples were compared to the results obtained on non-healed samples. This was done to investigate the self-healing capacity of each of the four types of bacteria.

2. Methodology

This project consists of three key components:

- i. *Bacteria*. As said, this study compared the healing potential of several types of bacteria. In particular, four bacteria genera were used: (i) *Bacillus subtilis* (B-14596), (ii) *Bacillus megaterium* (B-350), (iii) *Pseudomonas stutzeri* (B-2461), and (iv) *Sporosarcina pasteurii*.²⁴ Each bacteria group was grown via broth culture. Following the instructions provided by the Agricultural Research Service Culture Collection (ARS) at the North Regional Research Laboratory (NRRL), *B. subtilis*, *B. megaterium*, and *P. stutzeri* were grown in Tryptone-Yeast-Glucose broth (TYG broth), while *S. pasteurii* was grown in Ammonium-Yeast broth (NH₄-YE broth) as instructed by the American Type Culture Collection (ATCC).^{23,24}
- ii. *Biochar*. The biomass within the biochar acts as an immobilizer for the bacteria. This enhances the bacteria's healing efficiency.²⁷ In this study, food waste was used as biomass. The food waste included meat, butter, bread, rice, fruits, and salad. Starting from the data proposed in different research studies (see Figure 1) we aimed to replicate, at a smaller scale, the different food types of municipal wastes.²⁶ Thus, this study proposes an eco-friendly and low-impact method to recycle a large amount of a common type of waste.
- iii. *Concrete samples*. Concrete samples were tested under pure compression. A test protocol was designed to investigate the effects of bio-healing on the mechanical properties of the samples and to compare this response against that of samples without bio-healing.

The detailed descriptions of these three components are given in the following subsections.

2.1 Bacterial Media and Growth Conditions

Description of the cultures and their growth condition

B. subtilis (B-14596), *B. megaterium* (B-350), and *P. stutzeri* (B-2461) were provided by the Agricultural Research Service Culture Collection (ARS) at the North Regional Research Laboratory (NRRL) and were grown in the recommended TYG media, which includes 2 grams of Tryptone, 5 grams of yeast extract, 1 gram of dipotassium phosphate, and 1 gram of glucose within 1 L of deionized water. The TYG broth was subsequently autoclaved prior to downstream culturing.²³ *S. pasteurii* was obtained from the American Type Culture Collection (ATCC) and was grown in the suggested Ammonium-Yeast (NH₄-YE) broth, which was composed of 10 grams of ammonium sulfate, 20 grams of yeast extract, and 0.13 mol/L of Tris(hydroxymethyl)aminomethane (tris) buffer at pH 9.0 in 1 L of final volume.²⁴ Each

ingredient was separately sterilized by autoclaving prior to mixing. Table 1 displays the composition of TYG and NH₄-YE media.

Figure 1. Box and Whisker Plot of Percentage of Food Wasted by Group in Municipal Solid Wastes.²⁶

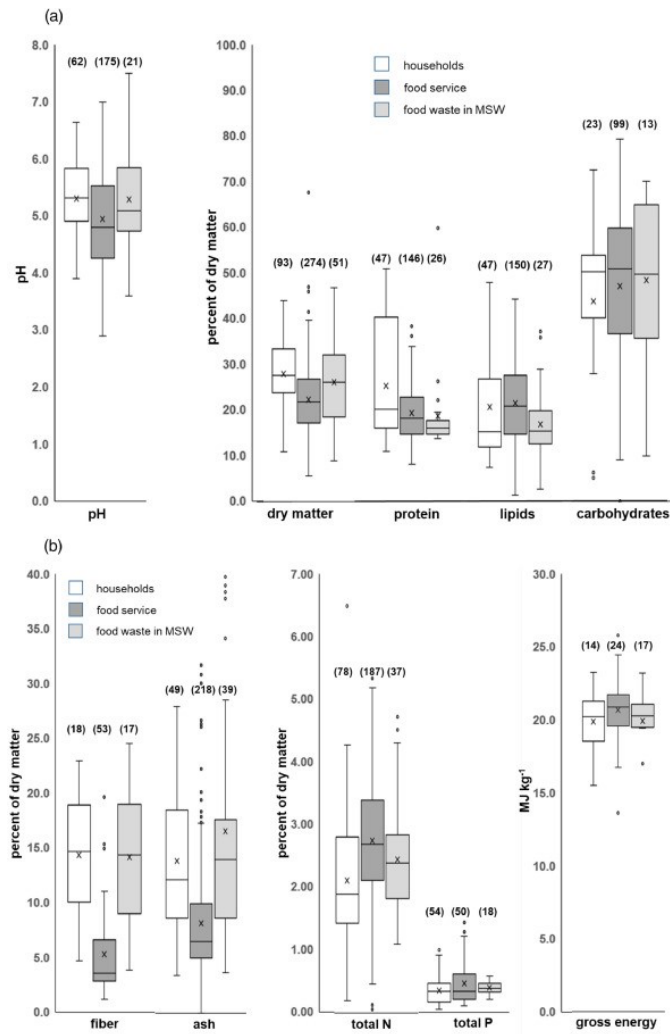


Table 1. Compositions of the two Broth Cultures Used For Bacteria Growth

Tryptone-Yeast-Glucose broth (1 L)	Ammonium-Yeast broth (1 L)
Tryptone (2 g)	Ammonium sulfate (10 g)
Yeast extract (5 g)	Yeast extract (20 g)
Dipotassium phosphate (1 g)	Tris buffer (0.13 M)
Glucose (1 g)	

Culture procedures and measurement

A sterilized pipette was used to transfer 35 mL of autoclaved broth into a 50 mL conical tube in a sterilized work environment. *B. subtilis*, *B. megaterium*, and *P. stutzeri* were transferred into tubes filled with TYG broth, while *S. pasteurii* was transferred into tubes of NH₄-YE broth using a sterilized inoculating loop. All types of bacteria grew aerobically at 28°C in an orbital incubator shaker for 24 hours or until growth was observed. The control TYG and NH₄-YE broths without bacterial cultures were also placed in the incubator for contamination verification.

A spectrophotometer was used to measure the optical density at 600 nm (O.D.₆₀₀) of the bacterial growth to confirm the growth of the bacteria in each vial. The O.D.₆₀₀ of 1 was maintained to standardize each bacterial cell number at each concrete manufacturer batch.

2.2 Biochar

Biochar is charcoal made from biomass. In this study, the biomass was provided by food waste. For this research, food near the expiration date was bought and transformed into charcoal as it was not possible to obtain food waste from the municipality. Nevertheless, the food for the biochar was mixed following the composition described in Figure 1. For the study, 20 L of biochar was produced. The food was cut up into pieces and put into a dehydrator to remove all moisture. After at least 24 hours, the food was removed from the dehydrator and checked to see if all moisture had been removed.

The dried food was then wrapped in aluminum foil and placed into a furnace at 300°C for 1 hour. Through this process, the food waste undergoes pyrolysis and turns into biochar. Finally, the resulting biochar was mixed in a large container.

2.3 Concrete

Description of the concrete samples

The manufacturing of the concrete samples is herein described. To manufacture the samples, the 90-lb (40.8 kg) QUIKRETE® ready-to-use concrete mix was used. This is a pre-blended mixture of cement and aggregates for general structural uses, requiring only the addition of water. The concrete was mixed in a Portable Concrete Mixer, with a 5 cu. ft. (0.14 m³) drum capacity, paired with a 1/2 HP motor, and a tilting/pivoting drum. As per the manufacturers' recommendations, 3.96 L of water was gradually added to the concrete mix, which was mixed for 5 minutes. More specifically, the first half of the water was poured in at the beginning of the process, and the remaining portion was poured halfway through the mixing process.

For samples C1 to C11, biochar was added with the water, during the mixing of the samples. The volume of the biochar was 5% of that of the wet concrete.

The concrete mixture was cast into 4" x 8" cylinder molds (101.6 mm x 203.2 mm) to obtain samples of the required dimensions. The ASTM C31 – Making and Curing Concrete Test Specimens in the Field procedures were employed for this scope.²⁵

Following ASTM C511 requirements, after an initial curing, all the concrete samples were positioned in curing tanks filled with water saturated with calcium hydroxide. All the tanks were located inside a curing room with a temperature within the 73.5°F, +/- 3.5°F range. During the initial curing, the cylinders were stored in a curing room and were not exposed to sunlight or heating for 48 hours. For all samples, curing in water lasted 28 days.

A total of 77 samples were manufactured and tested (see Table 2). The samples were subdivided into 7 sets of 11 samples each:

Set A, *Concrete samples to failure*, samples A1 to A11. This is the control set and consists of concrete samples tested up to failure after 56 days of curing. No self-healing procedures were applied to this set.

Set B, *No self-healing*, samples B1 to B11. These concrete samples are cracked after 28 days of curing and are tested to failure after an additional 28 days. These samples were not sprayed with bacteria after cracking (no self-healing) and have been used to investigate the influence of cracking on the ultimate response of concrete.

Set C, *Self-healing with biochar (no bacteria)*, samples C1 to C11. The samples of this set are cracked after 28 days of curing and tested to failure after an additional 28 days. Biochar was added to concrete during the mixing of the samples. The volume of biochar was 5% of that of wet concrete. After cracking, these samples were not treated with bacteria.

Set D, *Self-healing with B. subtilis*, samples D1 to D11. This set of samples is cracked after 28 days of curing and tested to failure after an additional 28 days; the samples were treated with *B. subtilis* after cracking.

Set E, *Self-healing with B. megaterium*, samples E1 to E11. This set of samples is cracked after 28 days of curing and tested to failure after an additional 28 days; the samples were treated with *B. megaterium* after cracking.

Set F, *Self-healing with P. stutzeri*, samples F1 to F11. This set of samples is cracked after 28 days of curing and tested to failure after an additional 28 days; the samples were treated with *P. stutzeri* after cracking.

Set G, *Self-healing with S. pasteurii*, samples G1 to G11. This set of samples is cracked after 28 days of curing and tested to failure after an additional 28 days; the samples were treated with *S. pasteurii* applied after cracking.

Table 2. Description of the Samples Manufactured for this Study

Set Name	Sample Names	Cracking at 28 days	Self healing protocol
Concrete samples to failure	A1 to A11	Not implemented	Not implemented
No self-healing	B1 to B11	Not implemented	Not implemented
Self-healing with biochar (no bacteria)	C1 to C11	implemented	Just biochar
Self-healing with <i>B. subtilis</i>	D1 to D11	implemented	implemented
Self-healing with <i>B. megaterium</i>	E1 to E11	implemented	implemented
Self-healing with <i>P. stutzeri</i>	F1 to F11	implemented	implemented
Self-healing with <i>S. pasteurii</i>	G1 to G11	implemented	implemented

Testing procedures

After curing, concrete samples were ready to be tested. Compression tests were performed at the College of Engineering of the California State University, Long Beach, using the Humboldt HCM-500-iHA Compression Testing machine (Figure 2a). This machine can apply a maximum vertical force of 2,224 kN, while the maximum piston stroke is equal to 63.5 mm. Figure 2b depicts concrete samples after being cracked.

The protocols used for the compression tests are described as follows.

Test protocol to determine the compressive strength of concrete

The testing procedure described in ASTM C39 was used to determine the compressive strength of concrete.²⁹ The curing time for each sample was 56 days. Sample Sets B to G were cracked after 28 days of curing before testing them to failure. The procedure used to create cracks in the samples is described below.

Test protocol to crack concrete samples (cracking at 28 days)

After an initial curing of 28 days, the samples of Sets C, D, E, F, and G were tested up to a compressive load equal to 75% of the average compressive strength of the samples of Set A. For this scope, the same loading rate used to determine the compressive strength of concrete was adopted up to 15.9 MPa, to then unload the samples. It is worth mentioning that while this testing protocol is sufficient to induce cracks in the samples, the pattern, width, and extension of these cracks will vary between samples. The procedure was deemed valid for the scope of this work as it allows for the rapid creation of cracks that would correspond to those present in highly strained concrete elements.

Test Protocol for self-healing

Immediately after cracking, the samples of Sets D, E, F, and G were set aside in a different non-leak tray. The samples were then poured with 50 mL of solution (Table 2):

Set D: *Bacillus subtilis*.

Set E: *Bacillus megaterium*.

Set F: *Pseudomonas stutzeri*.

Set G: *Sporosarcina pasteurii*.

These samples were then covered using a cling film and placed on a shelf in a curing room. The bacteria were three times: the first time after 24 hours from cracking, the second time after 48 hours from cracking, and the third time 72 hours after cracking, each time using 50 ml of the broth cultures described in Table 1.

Figure 2. (a) Humboldt HCM-500-iHA Compression Tester of the California State University Long Beach, (b) Concrete Samples after Cracking Test

(a)



(b)



3. Results

3.1 Average Compressive Strengths

The average compressive strength was assumed as a key parameter of the experimental tests. The average compressive strengths of the concrete samples of each set are shown in Figure 3. In this figure, $f_{cm}^{Set X}$ indicates the compressive strength of the variable Set X, with X varying from A to G.

As can be seen, the average compressive strength of the samples with no pre-cracking and self-healing (i.e., $f_{cm}^{Set A}$) was equal to 21.2 MPa. This value was assumed as the reference strength for the remaining sets. In Figure 3, $f_{cm}^{Set A}$ is compared with each $f_{cm}^{Set X}$ using green or red arrows, to indicate an increase or a decrease, respectively of the average compressive strength of the generic set.

Loading the concrete samples up to 75% of $f_{cm}^{Set A}$, unloading, and then reloading up to failure, reduces the average compressive strength of the set ($f_{cm}^{Set B}$) to 18.9 MPa (red arrow). Results on this set of samples' compressive strength demonstrated how cracking plays a key role in reducing the capacity of the concrete samples. As compressive strength is the most relevant property of the concrete, methods to prevent degradation of this parameter, such as the self-healing proposed in this study, are of great interest.

Set C samples are cracked after 28 days of curing and tested to failure after an additional 28 days. The average compressive strength of this set of specimens ($f_{cm}^{Set C}$) was equal to 12.0 MPa. This is the lowest value among all this study's sets of samples. As a result, biochar alone was found to have no healing properties on cracked concrete specimens.

Bacterial self-healing was applied to the last four sets, i.e., Sets D, E, F, and G. The average compressive strengths of these sets were found to be 22.5 MPa ($f_{cm}^{Set D}$), 15.6 MPa ($f_{cm}^{Set E}$), 21.7 MPa ($f_{cm}^{Set F}$), and 24.0 MPa ($f_{cm}^{Set G}$), respectively.

In Figure 3, the generic set's average compressive strength is compared to that of the control set (i.e., $f_{cm}^{Set X} / f_{cm}^{Set A}$). In this figure, the percentage increments ($f_{cm}^{Set X} / f_{cm}^{Set A} - 1 \geq 1$, green markers) or reductions ($f_{cm}^{Set X} / f_{cm}^{Set A} - 1 < 1$, red markers) obtained for the different sets are also shown and plotted on a secondary vertical axis.

From Set C to Set G, three out of four treatments with bacteria contributed to incrementing the average compressive strength of the concrete samples: (i) self-healing with *Bacillus subtilis* (Set D), (ii) with *Pseudomonas stutzeri* (Set F), and (iii) with *Sporosarcina pasteurii* (Set G), corresponding to +6.11%, +2.49%, and +13.5% of the strength of Set A, respectively. These results are encouraging, demonstrating how these low-cost and eco-friendly treatments can be a valid method to improve the mechanical properties of the concrete.

For the remaining sets, the average compressive strength reduces compared to the control set with a -43.1% reduction in Set C and -26.2% in Set E.

Figure 3. Average Compressive Strengths of the Different Set


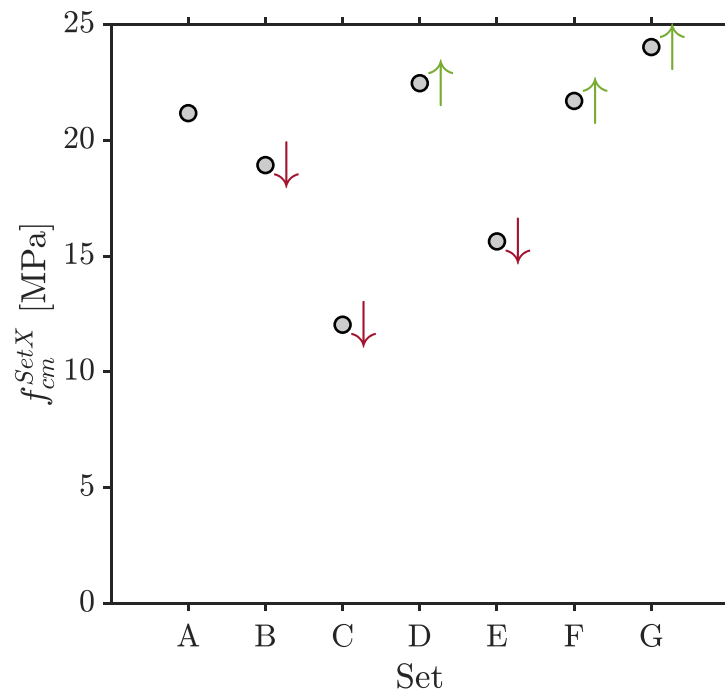


Figure 4. Percentage Variation of the Average Compressive Strengths of the Generic Set, Relative to Set A

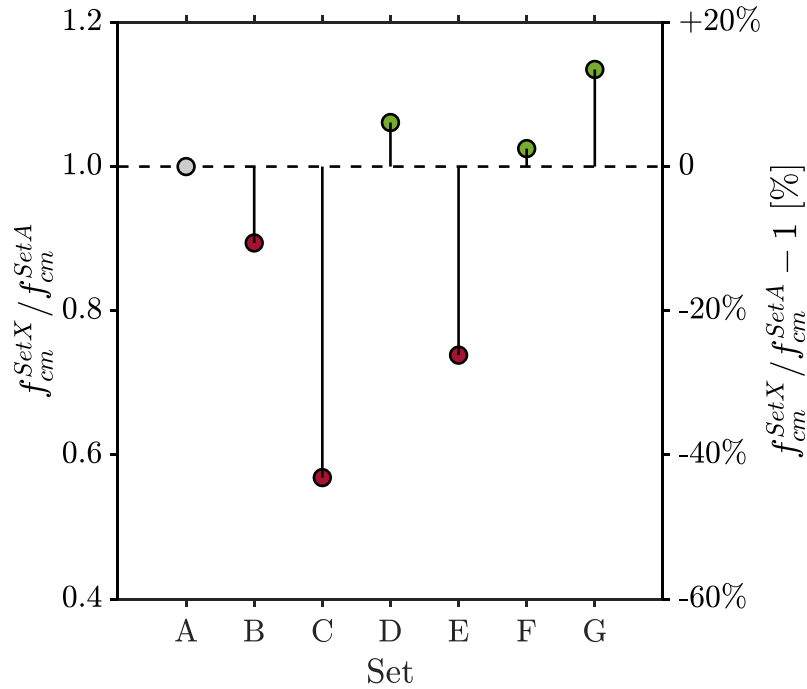

3.2 Variation of the Average Compressive Strengths

Figure 5 shows the average compressive strengths of the different sets with the corresponding standard deviations, calculated as:

$$\sigma_{Set X} = \sqrt{\frac{\sum_{i=1}^n (x_i - \bar{x})^2}{n-1}}$$

In Figure 5, the green and the red markers show how the generic $f_{cm}^{Set X}$ may be increased or decreased with respect to Set A. The numerical values of these quantities are also reported in the same figure.

The standard deviations of Sets B, C, D, E, F, and G were found to be equal to: 7.53 MPa, 3.62 MPa, 10.1 MPa, 8.32 MPa, 7.40 MPa, and 9.54 MPa, respectively.

Comparing the maximum values of compressive strengths (green markers of Figure 5) of Sets D ($f_{c,max}^{Set D}$), E ($f_{c,max}^{Set E}$), F ($f_{c,max}^{Set F}$), and G ($f_{c,max}^{Set G}$) with $f_{cm}^{Set A}$, shows how all the self-healing treatments can increase the average compressive strength of the control samples. However, larger standard deviation values were obtained for these sets compared as to Set A.

Figure 6 shows the coefficient of variation (c.o.v.) of each set of tested samples, obtained as:

$$\sigma_{Set X}^* = \frac{\sigma_{Set X}}{f_{cm}^{Set X}}$$

As can be seen, for samples treated with bacteria a minimum dispersion of the order of 30% is obtained for the sets. This dispersion may depend on the crack patterns of the concrete samples. As each specimen was cracked, treated, and then tested up to failure, the first loading protocol causes non-uniform cracks in the different specimens that have an impact on the mechanical properties of the samples and the effectiveness of the self-healing treatments. In future research, the variability induced by the cracking protocol should be addressed. To obtain uniform responses, independent of the failure mode of the specimen, it is necessary to control the cracks' formation upstream. A simple method could consist of using plastic or metallic inserts embedded inside the cylinder samples prior to casting. These shims could be removed after curing and would allow to test samples with same crack width, pattern, and dimensions.

Regarding the average compressive strength, the following *efficacy parameter* can be used to estimate the effectiveness of the treatment:

$$\psi_{Set X} = \frac{f_{cm}^{Set X} / f_{cm}^{Set A} - 1}{\sigma_{Set X}}$$

This parameter simultaneously considers the increase in compressive strength due to the self-healing treatment and the dispersion obtained for each set. Thus, larger values of $\psi_{Set X}$ correspond to more effective treatments, while negative values represent treatments that produce no improvements. The values of $\psi_{Set X}$ are shown in Table 3, where a summary of the main parameters discussed so far are also reported. As can be seen, self-healing with *Sporosarcina pasteurii* (Set G) appears to be the most effective treatment.

Figure 5. Average Compressive Strengths of the Different Sets with Standard Deviations


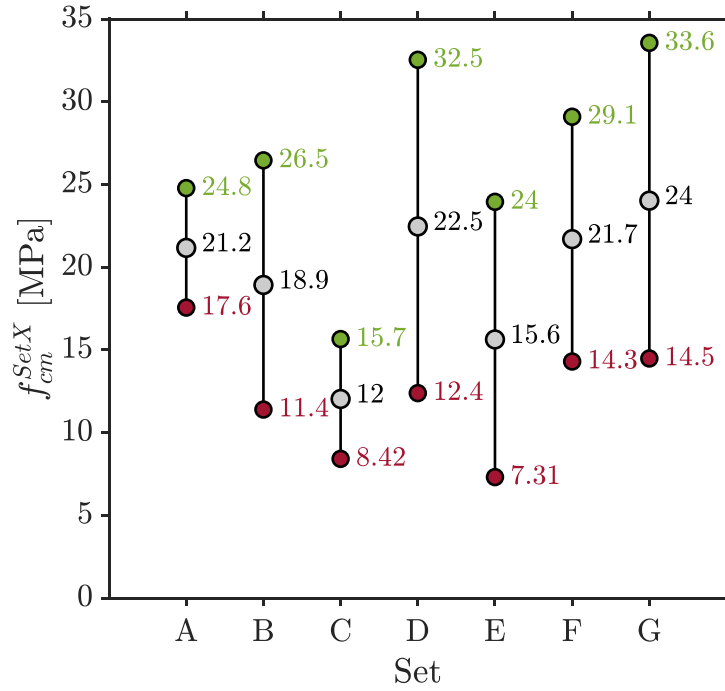


Figure 6. Coefficient of Variation off Each Set

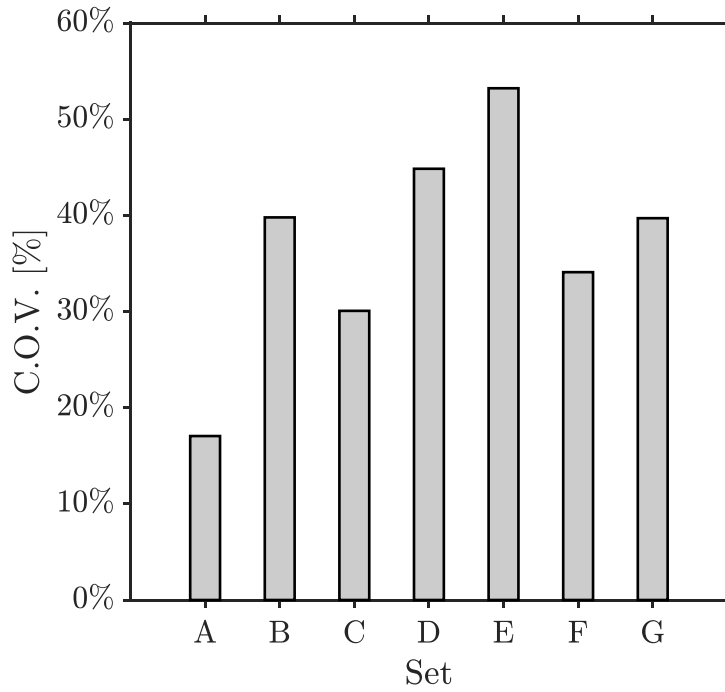

3.3 Elastic, Ultimate Response, and Ductility

The elastic limits of the concrete samples are herein calculated according to Fib Model Code, where the Serviceability Limit State (SLS) is identified within a compressive stress as $f_{cy,m}^{Set X} = 0.4 \cdot f_{cm}^{Set X}$.²⁸ Figure 7 shows the average values of these limits for each set, with the corresponding elastic compressive strain $\epsilon_{cy,m}^{Set X}$ (gray markers). In the same figure, the average values of the peak ($f_{cm}^{Set X} - \epsilon_{cm}^{Set X}$, black markers) and ultimate ($f_{cu,m}^{Set X} - \epsilon_{cu,m}^{Set X}$, red markers) compressive stresses—strains are plotted for a direct comparison.

Table 3. Summary of the Main Parameter Related to the Average Compressive Strengths

Set	f_{cm} [MPa]	σ [Mpa]	C.O.V. [%]	$f_{cm}^{Set X} / f_{cm}^{Set A}$ [%]	ψ
A	21.2	3.61	17.1%	0.0%	0.000
B	18.9	7.53	39.8%	-10.59%	-0.014
C	12.0	3.62	30.1%	-43.1%	-0.119
D	22.5	10.08	44.8%	6.11%	0.006
E	15.6	8.32	53.2%	-26.2%	-0.031
F	21.7	7.40	34.1%	2.49%	0.003
G	24.0	9.54	39.7%	13.5%	0.014

Starting from the values at the elastic limit and at the peak, the reduced modulus of elasticity $E_c^{Set X} = f_{cy,m}^{Set X} / \epsilon_{cy,m}^{Set X}$ and the modulus of elasticity $E_{cm}^{Set X} = f_{cm}^{Set X} / \epsilon_{cm}^{Set X}$ can also be calculated.²⁸ These values are plotted in Figure 8.


As expected, being loaded up to first cracking and then reloaded up to failure, the samples of Sets from B to G show greater vertical deformations compared to the control Set A (Figure 7). As a result, decreasing values of the elastic moduli of the same sets were also obtained (Figure 8).

As Section 3.2 shows, treatments with *Bacillus subtilis* (Set D), with *Pseudomonas stutzeri* (Set F), and with *Sporosarcina pasteurii* (Set G), increase the average compressive strength; the same treatments increase the limit elastic stress as well (Figure 7, gray markers). As for the ultimate responses, all sets return values of the stresses lower than Set A, but larger than the ultimate compressive strains (Figure 7, red markers). The ultimate compressive strain, a key parameter in building materials as it is related to ductility, is defined as:

$$\mu_{Set X} = \frac{\epsilon_{cu,m}^{Set X}}{\epsilon_{cy,m}^{Set X}}$$

The average values of the ductility are shown in Figure 9 for each set. In this figure, green markers represent sets of samples with average ductility greater than Set A, while red markers stand for reductions in ductility compared to Set A. The percentage increases/decreases of the ductility of the generic set compared to the control set are plotted in Figure 9 in the secondary axis. As shown, self-healing with *Bacillus subtilis* (Set D) and with *Sporosarcina pasteurii* (Set G) led to large increases of the average ductility of the concrete samples, equals to +25.8% and +49.6%, respectively; for the remaining self-healing treatments, slight reductions of the same parameter are obtained, corresponding to -2.85% for Set E and -3.04% for Set F.

Figure 7. Elastic, Peak, and Ultimate Stresses Vs. Strain of the Concrete Samples

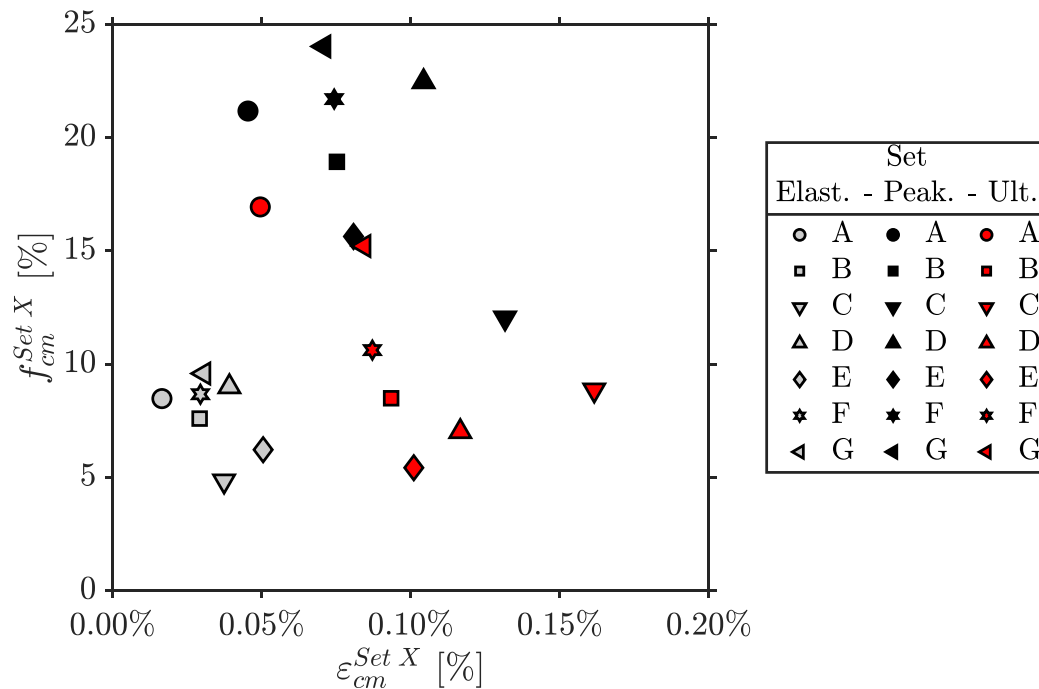

Combining the results obtained in Section 3.1 on the average compressive strengths with the results of this section on the concrete's ductility, the best self-healing procedure appears to be the one with *Sporosarcina pasteurii*. For this set of samples, a significant increase in ductility and a good improvement of the compressive strength were obtained.

Figure 8. Moduli of Elasticity of the Different Sets


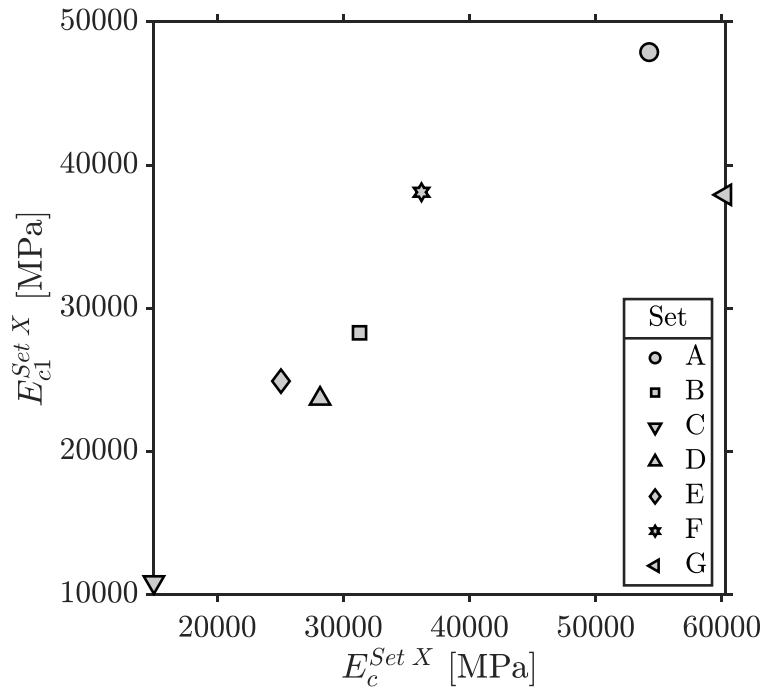


Figure 9. Average Ductility Values of the Concrete Sets

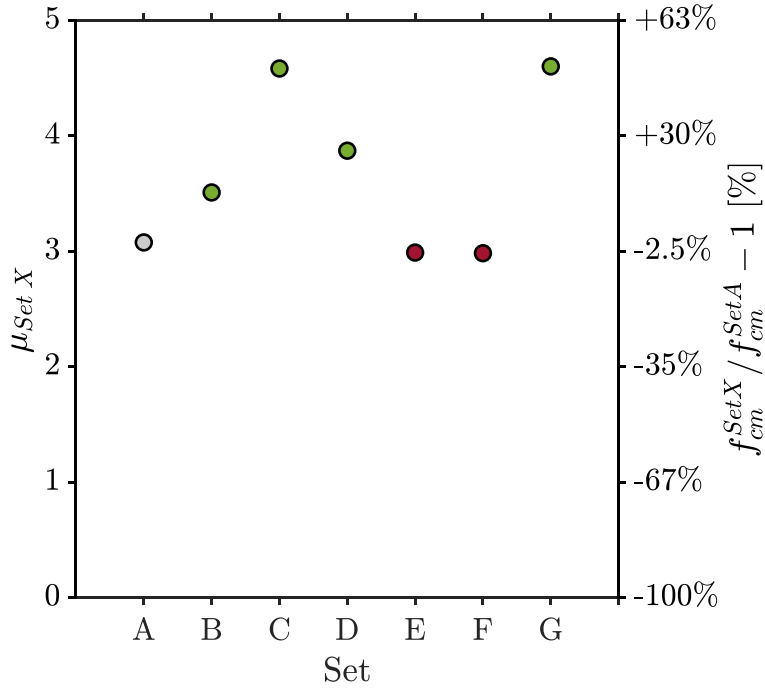

4. Conclusions

Durability of concrete structures is a significant topic in civil engineering. A significant research effort has been focused on the degradation phenomena of concrete, highlighting how these phenomena are significantly dictated by cracking of the material. The need to extend the durability of concrete infrastructures led to the development of several methods for improving the mechanical properties of cracked concrete.

This research work studied a low-cost and eco-friendly method to improve the durability of concrete using self-healing bacteria. Experimental compression tests were conducted on 7 sets of 11 concrete samples. The first two sets included samples with no treatments and were used as control samples; the remaining sets consisted of concrete samples treated with:

- Biochar (and no bacteria)
- *Bacillus subtilis*.
- *Bacillus megaterium*.
- *Pseudomonas stutzeri*.
- *Sporosarcina pasteurii*

The average compressive strength of each set was measured. The strength of the samples subjected to the self-healing procedures were compared to the compressive strength of the control set. Results showed how self-healing procedures with *Bacillus subtilis*, *Pseudomonas stutzeri*, and with *Sporosarcina pasteurii* increased the average compressive strength of the concrete samples, while the remaining self-healing procedure with *Bacillus megaterium* did not prove effective in increasing the mechanical properties of the material.

The standard deviation and the coefficient of variation of the compressive strengths were also reported for each tested set. These parameters showed how a slight dispersion resulted in computing the compressive strength of the single sample of the generic set as a result of the different failure modes observed during the experimental tests.

Finally, a discussion on the elastic and ultimate responses, as well as on the ductility of the concrete sets, was reported, showing how all the self-healing treatments increase the ultimate compressive strain of the samples, reducing the elastic moduli at the same time. The ductility of the concrete appeared to be improved by self-healing with *Bacillus megaterium* and *Sporosarcina pasteurii*, while *Bacillus subtilis* and *Sporosarcina pasteurii* played a minor role on this parameter.

The results of this work can contribute to the diffusion of sustainable concrete structures with the ability to fix its cracks autogenously or autonomously.

Endnotes

1. Mehta, P. K. and Moneiro, P. J. “Concrete: microstructure, properties, and materials,” 4, 2014.
2. Li, Z. *Advanced concrete technology*. John Wiley & Sons, 2011.
3. Boullenois, E. *Why does concrete crack? Part 1—The main reasons*, 21 March 2019, <https://blog.master-builders-solutions.com/en/reasons-why-concrete-cracks>.
4. Silva, F. B., Boon, N., Belie, N. D., and Verstraete, W. “Industrial application of biological self-healing concrete: Challenges and economical feasibility,” *Journal of Commercial Biotechnology*, 21 (1), 2015.
5. Van Tittleboom, K., and De Belie, N. “Self-Healing in Cementitious Materials: A Review,” *Materials*, 6 (6), 2013: 2182–2217.
6. Joshi, S., Goyal S., Mukherjee A., and Reddy M. S. “Microbial healing of cracks in concrete: a review,” *Journal of Industrial Microbiology and Biotechnology*, 44 (11), 2017: 1511–1525.
7. Van der Bergh, J. M., Miljevic, B., Šovljanski, O., Vucetic, S., Markov, S., Ranogajec, J., and Brás, A. “Preliminary approach to bio-based surface healing of structural repair cement mortars,” *Construction and Building Materials*, 248, 2022: 118557.
8. Sirico, A., Bernardi, P., Sciancalepore, C., Vecchi, F., Malcevschi, A., Belletti, B., and Milanese, D. “Biochar from wood waste as additive for structural concrete,” *Construction and Building Materials*, 303, 2021: 124500.
9. Sirico, A., Bernardi, P., Belletti, B., Dalcanale, E., Domenichelli, I., Fornoni, P., and Moretti, E. “Mechanical characterization of cement-based materials containing biochar from gasification,” *Construction and Building Materials*, 246, 2021: 118490.
10. Chen, X., Li, J., Xue, Q., Huang, X., Liu, L., and Sun Poon, C. “Sludge biochar as a green additive in cement-based composites: Mechanical properties and hydration kinetics,” *Construction and Building Materials*, 262, 2020: 120723.
11. Griño, A., Daly, M. M., and Ongpeng, J. “Bio-Influenced Self-Healing Mechanism in Concrete and Its Testing: A Review,” *Applied Sciences*, 10 (15), 2022: 5161.
12. Li, L., Zheng, Q., Li, Z., Ashour, A., and Han, B. “Bacterial technology-enabled cementitious composites: A review,” *Composite Structures*, 225, 2019: 111170.

13. Khaliq W., and Ehsan, M. “Crack healing in concrete using various bio influenced self-healing techniques,” *Construction and Building Materials*, 10, 2016: 249–357.
14. Muhd Afiq Hizami, A., Nurul Ain Harmiza, A., Mohamad Fahrurrazi, T. “Development and Performance of Bacterial Self-healing Concrete—A Review,” *IOP Conference Series: Materials Science and Engineering*, 431 (6), 2018: 062003.
15. Alexander, M., and Beushausen, H. “Durability, service life prediction, and modelling for reinforced concrete structures—review and critique,” *Cement and Concrete Research*, 122, 2019: 17–29.
16. Son, H. M., Kim, H. Y., Park, S. M., and Lee, H. K. “Ureolytic/non-ureolytic bacteria co-cultured self-healing agent for cementitious materials crack repair,” *Materials*, 11 (5), 2018: 782.
17. Jensen, O. M., and Hansen, P. F. “Autogenous deformation and RH-change in perspective,” *Cement and Concrete Research*, 31 (12), 2001: 1859–1865.
18. Guo, S., and Chidiac, S. “Self-healing concrete: a critical review,” *Durability of Structures*, In Proceedings of the 2019 CSCE Annual Conference, Laval, QC, Canada, 12–15 June 2019, <http://csceproceedings-ca.svr1-x-cd-com.vps.ezhostingserver.com/index.cfm?AbID=4152&CID=855#CSCEConf>
19. Lee, Y., and Park, W. “Current challenges and future directions for bacterial self-healing concrete,” *Applied Microbiology and Biotechnology*, 102 (7), 2019: 3059–3070.
20. De Belie, N. “Application of bacteria in concrete: a critical evaluation of the current status,” *RILEM Technical Letters*, 1, 2016: 56.
21. De Belie, N., and Wang, J. “Bacteria-based repair and self-healing of concrete,” *Journal of Sustainable Cement-Based Materials*, 5 (1–2), 2016: 35–56.
22. De Muynck, W., Boon, N., and De Belie, N. “From lab scale to in situ applications: the ascent of a biogenic carbonate-based surface treatment,” *In XIII International Conference on Durability of Building Materials and Components (XIII DMBC)*, 2014: 728–735.
23. Agricultural Research Service (NRRL) Culture Collection. “NRRL Medium No.1”, https://nrnl.ncaur.usda.gov/cgi-bin/usda/medium/1/nrrl_medium_1.pdf.
24. American Type Culture Collection (ATCC). *Sporosarcina pasteurii* (Miquel) Yoon et al. (ATCC 11859), <https://www.atcc.org/products/11859>.

25. ASTM Designation: C31/C31M—19. “Standard Practice for Making and Curing Concrete Test Specimens in the Field”, <https://dot.ca.gov/-/media/dot-media/programs/construction/documents/policies-procedures-publications/cpd/cpd20-2-attachment-3-astm-c31-c31m-19.pdf>.
26. Dou, Z. and Toth, J. D., “Global primary data on consumer food waste: Rate and characteristics—A review,” *Resources, Conservation and Recycling*, 168, 2021: 105332.
27. Gupta, S., Kua, H. W., and Dai Pang, S., “Healing cement mortar by immobilization of bacteria in biochar: An integrated approach of self-healing and carbon sequestration,” *Cement and Concrete Composites*, 86, 2018: 238–254.
28. Du Béton, Fédération Internationale. “fib model code for concrete structures 2010,” *Wiley-VCH*, (2013).
29. ASTM Designation C39/C39M-21. “Standard Test Method for Compressive Strength of Cylindrical Concrete Specimens”, https://www.astm.org/c0039_ce0039m-21.html.

Bibliography

- American Type Culture Collection (ATCC). *ATCC medium: 1376 Bacillus pasteurii NH4-YE medium*, 6 September 2022, <https://www.atcc.org/-/media/product-assets/documents/microbial-media-formulations/atcc-medium-1376.pdf?rev=5faecf5ce488437f807a717dcef980a0>.
- ARS (NRRL) Culture Collection. *Pseudomonas stutzeri*, 6 September 2022, <https://nrnl.ncaur.usda.gov/cgi-bin/usda/prokaryote/r-port.html?nrnlcodes=B-2461>.
- ARS (NRRL) Culture Collection. *Bacillus megaterium*, 6 September 2022, <https://nrnl.ncaur.usda.gov/cgi-bin/usda/prokaryote/report.html?nrnlcodes=B-350>.
- ARS (NRRL) Culture Collection. *Bacillus subtilis*, 6 September 2022, <https://nrnl.ncaur.usda.gov/cgi-bin/usda/prokaryote/report.html?nrnlcodes=B-14596>.
- Chen, L., et al. “Ammonium Removal by a Newly Isolated Heterotrophic Nitrification–Aerobic Denitrification Bacteria *Pseudomonas stutzeri* SDU10 and Its Potential in Treatment of Piggery Wastewater,” *Curr Microbiol*, 77 (10), 2020: 2792–2801, <https://doi.org/10.1007/s00284-020-02085-1>.
- Errington, J., and Aart, L. T. V. “Microbe Profile: *Bacillus subtilis*: model organism of cellular development, and industrial workhorse,” *Microbiology (Reading)*, 166 (5), 2020: 425–427, <https://doi.org/10.1099/mic.0.000922>.
- Goswami, G., et al. “*Bacillus megaterium* adapts to acid stress condition through a network of genes: Insight from a genome-wide transcriptome analysis,” *Scientific Reports*, 8 (1), 2018: 16105, <https://doi.org/10.1038/s41598-018-34221-0>.
- Lalucat, J., et al., “Biology of *Pseudomonas stutzeri*,” *Microbiology and Molecular Biology Reviews*, 70 (2), 2006: 510–547, <https://doi.org/10.1128/MMBR.00047-05>.
- Mortensen, B., et al., “Effects of environmental factors on microbial induced calcium carbonate precipitation,” *Journal of Applied Microbiology*, 111 (2), 2011: 338–349, <https://doi.org/10.1111/j.1365-2672.2011.05065.x>.

About the Authors

Pitiporn Asvapathanagul, PhD, PE

Dr. Pitiporn Asvapathanagul is a faculty member in Civil Engineering and Construction Engineering Management (CECEM) Department at California State University, Long Beach (CSULB). Her area of competence is Environmental Engineering, primarily bioremediation, biology wastewater treatment, and molecular biology. Examples of her research are bacterial community dynamics in activated sludge, nutrient removal of biological water reclamation processes, biofilms on aeration diffuser membranes, microplastic removal technologies, etc. Dr. Asvapathanagul is also a registered Professional Engineer (PE) in the state of California. Dr. Asvapathanagul employed her expertise in microbiology to advance accomplishments of the self-healing concrete project.

Simone Galano, PhD, Visiting Scholar

Dr. Simone Galano is a postdoctoral researcher at the University of Naples Federico II. He gained his PhD in Structural, Geotechnical, and Seismic Risk Engineering at the University of Naples Federico II in 2022. Since 2019, he has worked with the CSULB's CECEM Department as a visiting researcher. Dr. Galano's research activities are in the fields of seismic isolation with elastomeric devices, prestressed concrete structures, and the durability of existing prestressed concrete bridges. He authored many research studies including experimental tests and numerical analyses of fiber reinforced elastomeric isolators with natural, recycled, and reclaimed rubber, and reduced-scale post-tensioned concrete bridge girders.

For this project, Dr. Galano elaborated the experimental data, wrote the draft, and reviewed the final version of this report.

Andrea Calabrese, PhD, ING, CENG, MICE

Dr. Calabrese joined the CSULB's CECEM Department as an Assistant Professor in Fall 2017. He gained a PhD in Construction Engineering with an emphasis in Structural Engineering in 2013. He was a visiting research fellow at the Pacific Earthquake Engineering Research Center (PEER) from 2010–2012 along with having been a postdoctoral researcher of the ReLUIS Consortium at the Italian Network of University Laboratories in Earthquake Engineering from 2013–2014. Dr. Calabrese has worked as a Structural Engineer at Foster & Partners (London) and for other firms in Italy for seven years. He has been a registered engineer in Italy since 2009 and a Chartered Engineer (CEng) and Full Member of the Institution of Civil Engineers (MICE) in the UK since 2017. Dr. Calabrese's current research interests are in the fields of experimental testing, structural dynamics, base isolation, vibration engineering, and the development of novel low-cost devices for the seismic protection of buildings. He has carried out numerous large-scale

experimental studies of base isolation systems and energy-absorbing devices on the shaking table at the Department of Structural Engineering at the University of Naples in Italy. This work has been instrumental in developing low-cost seismic isolation systems using recycled rubber and flexible reinforcements for the seismic protection of buildings in developing regions.

His responsibilities for this research included conceptualization of the work, data analysis, and final editing of the report.

Mehran Rahmani, PhD, PE

Dr. Mehran Rahmani is an Assistant Professor in the CECEM Department at CSULB. He earned his PhD in Structural and Earthquake Engineering from the University of Southern California (USC) in 2014. His research focuses on structural system identification, structural health monitoring, and earthquake damage detection of buildings and bridges using sensory data. Dr. Rahmani is a registered Professional Engineer (PE) in the state of California.

In this project, Dr. Rahmani was responsible for training the research team for using the testing equipment, helping to design the concrete testing protocol, troubleshooting testing equipment hardware and software issues, and overseeing the concrete cylinder testing process.

Maggie Ly, Research Assistant

Maggie Ly is a post-graduate student in the CECEM Department at CSULB. She graduated with a BS in Civil Engineering in Fall 2019 at the same university and began pursuing her MA in Fall 2020. During her time as an undergraduate student, she assisted Dr. Pitiporn Asvapathanagul in performing research tasks relating to identifying bacteria in wastewater in the Environmental Engineering Laboratory. Subsequently, Maggie decided to work on her thesis “Applying...” under Dr. Asvapathanagul’s supervision.

Maggie was responsible for culturing bacteria, forming biochar using food wastes, manufacturing concrete test samples, landing bacteria in the concrete, and running tests on the concrete samples.

Daniela Flores, Research Assistant

Daniela Flores is an undergraduate research student in the Mathematics and Statistics Department at CSULB. She is pursuing a degree in Applied Mathematics with a focus in science and engineering.

Her responsibilities in this study consisted of the manufacturing and testing of the samples and contributing to writing the report.

Michael Hernandez, Research Assistant

Michael Hernandez is an undergraduate research assistant at the CSULB CECEM Department. He is pursuing a degree in Mechanical Engineering.

His responsibilities included assisting in the manufacturing and testing of samples. He also contributed to writing the draft and editing the final version of the report.

Nicholas Banuelos, Research Assistant

Nicholas Banuelos is an undergraduate student at the CSULB studying Environmental Science and minoring in Biology and Geography. His responsibilities included assisting in the manufacturing and testing of samples.

MTI FOUNDER

Hon. Norman Y. Mineta

MTI BOARD OF TRUSTEES

Founder, Honorable Norman Mineta***
Secretary (ret.),
US Department of Transportation

**Chair,
Will Kempton**
Retired Transportation Executive

**Vice Chair,
Jeff Morales**
Managing Principal
InfraStrategies, LLC

**Executive Director,
Karen Philbrick, PhD***
Mineta Transportation Institute
San José State University

Winsome Bowen
President
Authentic Execution, Corp

David Castagnetti
Partner
Dentons Global Advisors

Maria Cino
Vice President
America & U.S. Government
Relations Hewlett-Packard Enterprise

Grace Crunican**
Owner
Crunican LLC

Donna DeMartino
Retired Transportation Executive

John Flaherty
Senior Fellow
Silicon Valley American
Leadership Form

Stephen J. Gardner*
President & CEO
Amtrak

Rose Guilbault
Board Member
San Mateo County
Transit District (SamTrans)

Kyle Christina Holland
Senior Director,
Special Projects, TAP Technologies,
Los Angeles County Metropolitan
Transportation Authority (LA Metro)

Ian Jefferies*
President & CEO
Association of American Railroads

Diane Woodend Jones
Principal & Chair of Board
Lea + Elliott, Inc.

Therese McMillan
Retired Executive Director
Metropolitan Transportation
Commission (MTC)

Abbas Mohaddes
CEO
Econolite Group Inc.

Stephen Morrissey
Vice President – Regulatory and
Policy
United Airlines

Toks Omishakin*
Secretary
California State Transportation
Agency (CALSTA)

Marco Pagani, PhD*
Interim Dean
Lucas College and
Graduate School of Business
San José State University

April Rai
President & CEO
Conference of Minority
Transportation Officials (COMTO)

Greg Regan*
President
Transportation Trades Department,
AFL-CIO

Paul Skoutelas*
President & CEO
American Public Transportation
Association (APTA)

Kimberly Slaughter
CEO
Sysra USA

Tony Tavares*
Director
California Department of
Transportation (Caltrans)

Jim Tymon*
Executive Director
American Association of
State Highway and Transportation
Officials (AASHTO)

* = Ex-Officio
** = Past Chair, Board of Trustees
*** = Deceased

Directors

Karen Philbrick, PhD
Executive Director

Hilary Nixon, PhD
Deputy Executive Director

Asha Weinstein Agrawal, PhD
Education Director
National Transportation Finance
Center Director

Brian Michael Jenkins
National Transportation Security
Center Director

